



IM

By Lake Barrett and Heather Ramsey, Sauereisen, Inc.

Many regard the selection of floor coatings as an uncomplicated process. One can simply go to the nearest big box store and ask for a recommendation or just pick up what looks like it will work. Others realize there is more to the coating selection process and therefore develop specifications—some good, some not so good. Weak specs often result when key steps in the selection process are overlooked.

This article discusses the key steps

that should be taken while developing the protocol for a concrete flooring project. Within these steps are criteria that need to be addressed by one or all parties involved with the job. Some of these criteria may include substrate degradation, moisture within the substrate, surface preparation, application considerations, and chemical resistance and physical properties of the flooring material. Additionally, standardized references should play a role throughout the entire job process. Finally, case histories of differing applications are presented and discussed. This article gives an overview of the subject, not a comprehensive discussion.

Selecting Flooring for Concrete:

Background

Many times the difference between a successful floor-lining project (i.e., one with a good service life) and an unsuccessful one (that fails prematurely) can be reduced to five steps. The following steps are instrumental in the development and completion of the floor-coating project.

- Pre-project inspections of existing facilities
- Specification development
- Development of an appropriate floor coating selection process
- Selection of a qualified and well-trained applicator
- Establishment of and adherence to an appropriate quality control /quality assurance (QC/QA) process, including technical service from the lining system manufacturer

Each step will be discussed briefly.

Pre-project Inspections of Existing Facilities

All parties associated with the project should inspect the facility before the project begins. All of the parties—design engineers, architects, contractors, and a representative of the lining manufacturer—are stakeholders in the project and must exhibit the required commitment to its success. Their inspection of the site is a beneficial first step to understanding the scope and magnitude of what is required for a successful project.

The areas to be lined should be exam-

An Overview of What Not to Overlook

ined for abnormalities such as obvious surface defects and areas of contamination. Failed linings that may still be in place can be looked at closely and potential problem areas can be noted.

Particular attention should be paid to evidence of moisture or ground water infiltration. Detailed questions can be asked of the operators regarding these aforementioned items and others. Information pertaining to the exposure conditions for the lining system, such as exposure frequencies, spill procedures, and general cleanup methods, should be obtained. All parties should also develop an overall view of the work to be performed.

Specification Development Is Critical

A poorly written specification, or, equally bad, an inappropriate specification, can doom the project to a premature failure before the first craftsman appears on the site. The specification development process must take into consideration the substrate along with its condition and history. The quality and age of

the concrete are vital factors to address. Potential problems such as ground water and substrate settlement or movement (including excessive vibration) must also be examined.

Additionally, choosing an inappropriate reference standard or a test method, such as an ASTM test method, for a given material can preclude a successful installation. The mechanical properties of the material used not only have to be project specific, but must also have appropriate limits set for the expected physical forces. For example, specifying 20,000-psi compressive strength for a 45-mil coating on a floor subjected to significant thermal changes and abrasion, but not subject to a compressive load is inappropriate. The appropriate properties to evaluate for this example are coefficients of thermal expansion of the floor and the lining materials, flexural strength, flexural modulus of elasticity (MOE), tensile strength, bond strength, and abrasion resistance. In fact, a high compressive strength may be indicative of a material that is too rigid to perform as required.

The specification must include not only material requirements, but requirements on the abilities and training of all applicators. It must also delineate the required inspections, inspection points, test methodologies to be used, and pass/fail criteria of those tests.

Floor Coating Selection Process

The selection process may involve more than the specifier alone choosing material. It may not be possible for the specifier to determine the suitability of a given material based upon published chemical resistance data or from anecdotal claims. ASTM test methods and standards for chemical resistance of these materials do not specify pass/fail criteria. One manufacturer may interpret the results very conservatively and cautiously; however, another may be less

Selecting Flooring for Concrete:

conservative. The best recommendation may well be difficult to discern.

The specifier needs to not only ask for the above types of information, but also request the case histories of previous projects where similar exposures or application conditions existed. A reputable manufacturer or applicator will provide this information.

Sometimes, however, you will be, as the old saying goes, "The first to eat the oyster." That is, periodically the product that appears to be best suited has no relevant track record or it is so new that it has no track record at all. This situation is where the selection process must require verification of all relevant properties. The lining manufacturer should provide the data, their pass/fail limits, and the test methods used. Finally, the selection process must ensure that the test methods used are those prescribed by ASTM

and other authorities for those material types. For example, do not allow plastic test methods for a coating and do not use steel substrate test methods for the evaluation of a concrete substrate.

Selecting a Contractor

This step is frequently the determinant in the degree of success obtained with the overall project. A great contractor may not be able to make the wrong product work and conversely, a poorly trained and unqualified applicator may have success-threatening problems even if the correct material is selected.

It is crucial to examine the history of the contractor firm and its applicators. Ideally, the contractor/applicators would have 15 to 20 years of experience in general flooring application experience and five or more years of application experience

with the specified type of flooring. Additional qualifications might include SSPC-QP 8, "Standard Procedure for Evaluating the Qualifications of Contracting Firms That Install Polymer Coatings or Surfacing on Concrete and Other Cementitious Surfaces," and a letter of certification by the material manufacturer.

Quality Control/Quality Assurance (QC/QA) Process

The QC/QA process involves more than a program to inspect and/or test materials installed. The QC/QA program must cover substrate inspection and testing where necessary or required, as well as the surface preparation. The QC/QA process also ensures that the applicator stores, mixes, and applies the materials in accordance with the manufacturer's instructions. The applicators must

Selection, Application, and Performance

One of the nation's leading cereal suppliers had a 150,000-squarefoot food processing facility in dire need of repair. The facility's floor was approximately 10 years old and was suffering from the effects of heavy-duty forklift traffic as well as daily cleaning with aggressive chemicals. The concrete was spalled and cracks were evident throughout the facility. Because this area manufactured foods for human consumption, the floor needed to meet the requirements imposed by the U.S. Government's Food and Drug Administration (FDA).

Beyond meeting FDA requirements, the need for long-term performance was paramount; \$10,000 worth of product is produced per hour so shut-down is extremely costly. The facility dedicated a small team of managers to explore the product offerings of the largest flooring manufac-



Surface Preparation
(first of two passes)

Photos courtesy of the authors

turers in North America. They looked at multiple resins systems, including urethane mortars and epoxy flooring systems. After a critical analysis, a 100% solids hybrid epoxy lining was selected for its physical strength, chemical resistance, and the quality reputation of the manufacturer.



Application by hand trowel

The facility selected a qualified contractor, and together, the facility representative and contractor, along with the lining manufacturer, developed a protocol to minimize the impact on the plant by applying the flooring system in three distinct phases. Because the hybrid epoxy system is 100% solids, the contamination impact on existing lines was limited and the impact on the production of the facility was minimal.

The existing coating on the concrete was removed by shot blasting, and the edges were treated with small hand grinders utilizing cup stones and diamond grinders. The concrete was prepared in accordance with



THE PROTECTIVE COATINGS PROFESSIONALS™

We Build Trust With Linings That Stand The Test Of Time



1-888-CARBOLINE • www.carboline.com

Click our Reader e-Card at paintsquare.com/ric

demonstrate the required competency to properly install the protective system specified. This certification and qualifications usually require an on-site demonstration with appropriate QC testing of the applied system. The QC/QA process should involve technical service provided by the lining manufacturer (as specified) and direct communication among the manufacturer, the applicator, and project management. Final inspection should occur with a physical walkthrough by all interested parties for final acceptance.

Case Histories

Case histories often provide important information for all parties and should be required submittals in the pre-bid process. The case histories should be examined for relevance to the project at hand, application condi-

tions and methods, ease of installation, performance, maintenance requirements, service life, costs, and owner satisfaction. Examples of some of the kinds of information that case histories can provide are reflected in the cases on pp. 36–37 (below) and p. 40.

Flooring Systems


Floors are exposed to just about everything handled or produced at any given facility. Whatever comes into the facility or is made in the facility will probably come into contact with the floors at some point, by accident or otherwise. Process area floors and secondary containment floors often are subject to the most aggressive exposures, especially chemicals. Several types of floor lining systems can be used to protect concrete. Some of the most common types are described briefly below.

Organic Systems

Thin- and thick-film organic systems are the most commonly used materials for protecting floors. The available chemistries include bis A epoxies, bis F epoxies, novolak epoxies, polyesters, bis A vinyl esters, novolak vinyl esters and polyurethanes. (Inorganic alkali silicates, calcium aluminates and furans do not make good candidates for thin film linings.) Organic linings are typically applied at thicknesses ranging from a few mils to one inch and are bonded to the concrete either by direct bond or a primer. The systems can be formulated into trowelable toppings, sprayable linings, pour and spreads, or even for brush or roller application. The organic systems above offer ease of use, low permeance, excellent chemical resistance and, depending upon the thickness and the particular formula-

Continued on p. 39

History of a Floor Coating in a Food Plant

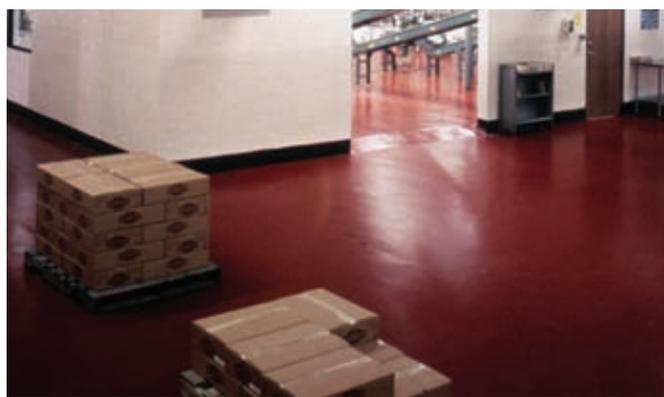

Finished Floor (Red)

SSPC-SP 12, and received a surface profile similar to a CSP-6 as described in the International Concrete Repair Institute, Guideline # 3732.

A 100%-solids penetrating primer was applied with a rubber squeegee and back-rolled with a short mohair roller to ensure complete wet-out of the concrete substrate. The areas subjected to heavy forklift abuse in conjunction with the organic acids received a one-quarter-inch-


thick overlay of a hybrid novolac epoxy system, which was applied by hand and power troweling. The finely blended aggregate within the floor topping system was intended to provide exceptionally consistent compaction, which would result in superior abrasion and impact resistance. The proprietary mix of rounded and angular constituents provided a surface that exceeds OSHA's slip resistance requirements (coefficient of friction) while preserving the system's ease of cleanliness.



Finished Floor (Grey)

The flooring systems were recently inspected after their 15th year, and although the system has lost its gloss, and areas subject to UV rays have faded a bit, the flooring system is fully functional, and the customer continues to be very pleased.

DEMAND Tough Machines

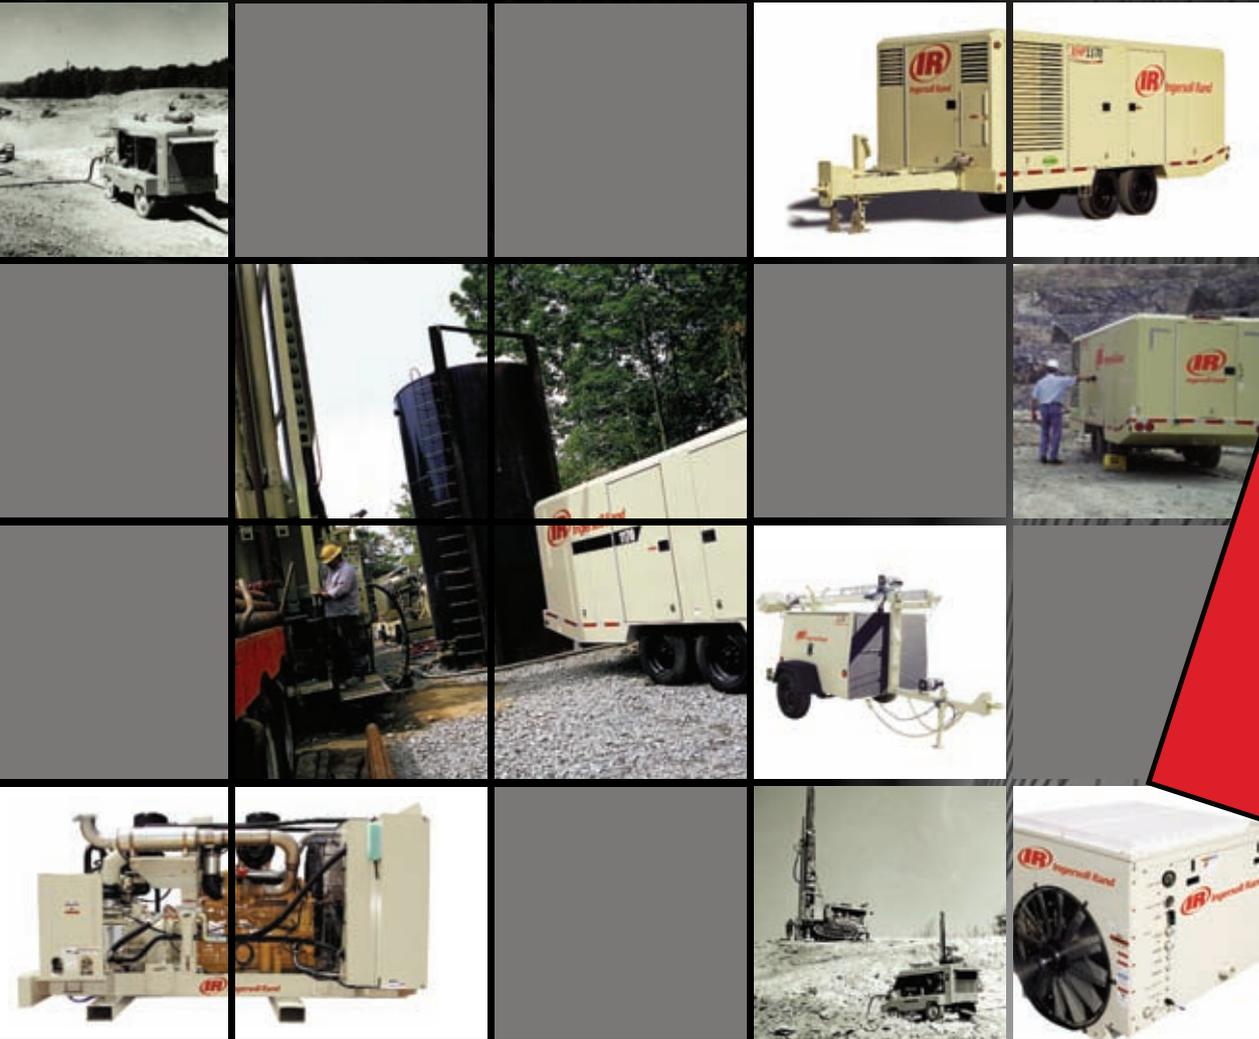

doosanportablepower.com
(877) 472-7263

© 2009 Doosan Infracore International, Inc.

Click our Reader e-Card at paintsquare.com/ric



Doosan Infracore
Portable Power

tion, good to excellent physical abuse protection as well.

Masonry

Masonry brick and masonry flooring systems have been used for centuries. When combined with 21st century technology, the systems provide excellent long-term durability in a number of physical and chemically demanding environments. This flooring type utilizes brick or tile and a setting-bed, grout, and/or mortar material to bond the masonry unit and floor. Both the masonry unit and setting material are chosen specifically for the chemical environment of the job.

Several types of brick are commonly used, such as Type I, II, and III acid-

resistant brick and carbon brick. These brick materials must conform to the physical requirements of ASTM C279: *Standard Specification for Chemical Resistant Masonry Units*. The differences among Type I, II and III acid-proof brick are their chemical resistance and degree of absorption, though all three are made from clay, shale, or mixtures of the two. Type II and III brick are used mostly for acids, whereas carbon brick is employed when hydroxides and hot alkalis make up the chemical environment (see ASTM C1160: *Standard Specification for Chemical-Resistant Carbon Brick*).

The specifications regarding tile, however, cannot be assumed to be the same as brick. The physical and chemi-

cal requirements of tile are listed in ASTM C126: *Standard Specification for Ceramic Glazed Structural Clay Facing Tile, Facing Brick, and Solid Masonry Units*. Several grades and types of tile may suit the contractor's needs. Tile is usually never thicker than three-quarters of an inch, whereas brick is greater than three-quarters of an inch. Tile is installed over a setting-bed and then grouted into place where the setting-bed and grout do not have to be the same material and usually are not. When brick is being used, however, the setting bed and grout are usually always the same material.

Furthermore, when using brick, a membrane material is first applied

**Finding the best
equipment for the job
have you in a fog?**

**We've been there
and we can help!**



2200 Van Deman St Suite 800 Baltimore MD 21224
866.CALL.ADI (225.5234) 410.631.1870
www.calladi.com

Specializing in:

*Blast Grit Recyclers
Dust Collectors
Vacuum Systems*

*Trailer mounted or
Skid models*

*Product upgrades,
Retrofits, and Service
for all brands*

*New and used rentals
Replacement parts*

*Visit us in New Orleans
at Pace 2009
Feb 15th - 18th
Booth 450*

Selecting Flooring for Concrete:

directly over the floor before the setting bed to ensure better chemical resistance. There commonly is no membrane under the setting-bed when applying tile due to the decreased load bearing ability of tile as compared to brick. There are also

several different types of setting-beds, grouts, and mortars one can use that include furan resins, asphaltic membranes, epoxies, vinyl esters, and even inorganic silicate based cements. Again, the chemical environment as well as the intended use and applica-

tion all play a part in choosing a material.

Polymer Concretes

Polymer concretes can be formulated with inorganic ceramic-based poly-

Continued on p. 42

Rehabbing an Unloading Area for a Petrochem Plant

Along the Gulf of Mexico, a Fortune 500 petrochemical facility processes extremely aggressive chemicals in an effort to maximize profits and minimize environmental impact. The truck unloading area where the raw materials are received was in very poor condition, as evidenced by a degraded coating and the chemically attacked concrete beneath it. This dilapidation created a dangerous situation because forklifts and other vehicular traffic would pass over the potholes in the slab several times throughout the day.

To provide a remedy, plant and environmental compliance engineers met to devise a procedure for rehabilitating the chemical unloading slab. A list was prepared, with each chemical cataloged including its storage temperature and concentration. The chemical configuration resembled a



*Constructing forms after surface preparation
Photos courtesy of the authors*

“witches brew,” but, fortunately, the blend of acids, solvents, and caustics were stored at ambient temperatures below 110 F (43 C). In addition to frequent splash and spill of chemicals, the slab is exposed to physical abuse in the form of forklift and 18-wheel truck traffic. Also, the material hoses that many of the chemicals are pumped through are frequently dropped directly on the slab. Due to the variety of chemicals used in the area, a vinyl ester polymer was chosen. Because of the unique nature of this application and the aggressive chemicals, only three manufacturers were considered and the list of qualified contractors was even shorter.

A project-specific specification was drafted. Input from the manufacturer, contractor, and a third-party inspector were all incorporated. A pre-job site meeting was held 30 days prior to the start of the installation to finalize all project plans. At this point, a tentative project schedule was devised, which included the number of workers required each day, along with contingency plans and a defined safe-

ty protocol. A primary goal on this project was to minimize downtime. The installation began with a pressure wash, followed by cleaning with an industrial cleaner/degreaser to ensure no contaminants would be forced into the slab during the abrasive blasting operation. The floor slab was blasted using an aluminum oxide aggregate to aggressively prepare the surface. A cementitious concrete repair material was chosen to fill in several large depressions (>3 inches deep) in the concrete slab. Fortunately, petrographic analysis was conducted and the results, although not perfect, were very promising overall. The petrographic analysis revealed inherent weakness not visible to the eye. Each crack and joint was routed out with an electric chipping gun and filled with a flexible, chemical-resistant joint filler.



Finished flooring project

Once the cracks and joints were properly addressed, refractory anchors were set into the prepared concrete on 12-inch centerlines. The purpose of the anchors is to help secure the chemical-resistant castable polymer overlay to the substrate. The entire slab area was then formed up into 12 ft x 12 ft sections. Each section would receive a 1.5-inch thickness of a wet-applied polymer overlay. Figure 1 illustrates the surface preparation and forming. Between the slabs, a chemical-resistant expansion joint material would be applied.

The vinyl ester polymer was installed next. A resin and hardener were pre-mixed, then transferred into a mortar mixer, where a select blend of aggregates were added and mixed until a uniform consistency was achieved. The mixed material was poured into the forms, then screed and finished with steel trowels. These materials handle very similarly to Portland cement concrete mixes, but do not require a protective coating.

Before pouring the slab, workers used the same polymer material to pour in place a sump, which collects all spills. The sump hardened in two hours and the contractor proceeded to pour the slab. Thus far, after three years, no problems, failures, cracks, or deteriorations have been reported.

FROM DETECTION TO CORRECTION:

Corrosion Probe, Inc. has the Most Concrete Coatings Experience and Expertise

We Have More Concrete, Corrosion and Materials
Engineering Experience Than Any Other Firm

- Corrosion Control Programs
- Civil/Structural Engineering/Design
- Non-Metals Materials Engineering
- Metallurgical Engineering
- Coatings/Linings Specifications
- Field & Laboratory Testing
- Mechanical Integrity Evaluation
- QC/QA Inspection Services

**Your Concrete
Rehabilitation and
Corrosion Control
Specialists**



CORROSION PROBE, INC.

Contact Us:
Phone: (860) 767-4402
Email: nixonr@cpiengineering.com
www.cpiengineering.com

Click our Reader e-Card at paintsquare.com/ric



ADVANCED
RECYCLING
SYSTEMS

Top-quality Equipment, Unequaled Customer Service

Brand New Units Available Now!


Rent-to-own or Try-before-you-buy!

abrasive recyclers



- 6-nozzle, 4-nozzle or 2-nozzle units

wireless blasting

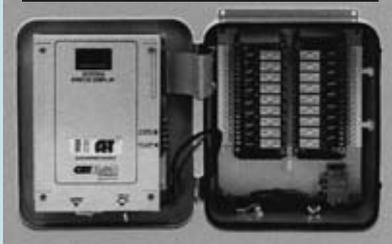

- no wires from recycler to containment
- no downtime searching for cut/broken wire

Need waste bags? Salt? Vacuum hose? Dust collector hose? Other accessories? Call for lowest prices!

Contact us today to discuss all your equipment needs!

Tel: 330.536.8210 • www.arsrecycling.com • Fax: 330.536.8211

sales • rentals • leases • upgrades • repairs • parts • accessories

Click our Reader e-Card at paintsquare.com/ric

Selecting Flooring for Concrete:

Table 1: Relative Comparison of General Properties of Various Flooring Types*

FLOORING TYPE	CHEMICAL RESISTANCE				PHYSICAL PROPERTIES				
	Acids		Caustics	Solvents	Abrasion resistance	Compressive strength	Flexural strength	Longevity	Cost
	Organic	Inorganic							
Portland-Based Cement	F	F	C	C	B	B	D	C	\$
Bisphenol A Epoxy	C-A	C-A	A	C	A - C	A-C	B	B	\$\$
Bisphenol F Epoxy	B-A	B-A	A	B	A-C	A-C	B	B	\$\$
Novolac Epoxy	A	A	A	A	A-C	A-C	B	B	\$\$\$
Bisphenol A Vinyl Ester	C-A	C-A	B	B	A-C	A-C	B	B	\$\$\$
Novolac Vinyl Ester	A	B	B	A	A-C	A-C	C	A	\$\$\$\$
Polymer Concrete	A	A	A-B	A	A	A	B	A	\$\$\$
Brick	A	A	B	A	A	A	B	A	\$\$\$\$

* Key **A** – Best **B** – Better **C** – Good **D** – Marginal **F** – Not Recommended **\$\$\$\$** - Most Expensive **\$\$\$** - **\$\$** - **\$** - Least Expensive
 This rating system is relative and not intended to be quantitative.

mers, such as potassium silicate, or from organic resins, such as epoxies, vinyl esters, polyesters, and even furans. These products offer several advantages over masonry linings and coatings. Installation of polymer concretes is similar to Portland cements and, therefore, polymer concretes are

faster and easier to install than masonry linings. Polymer concretes offer equal or even superior physical properties and service lives compared to masonry. The chemical resistance of polymers is equivalent to or better than masonry and their permeance is extremely low. Due to their mass and

composition, polymer concretes are far more durable than coatings and linings. Using polymer concretes, usually at one-third to one-half of the thickness required for Portland concrete, eliminates the need to line or coat concrete in order to protect it, so

Continued on p. 45

Overspray Problems? We Have the Solution!



DAMAGE CONTROL: Control overspray costs through our fast, professional overspray removal service, guaranteed to minimize claims.

COMPETITIVE PRICING: Realistic pricing without additional charges for travel or accommodations.

EXPERIENCE: Forty-two years of experience removing paint, epoxies, urethanes, asphalt, tar, concrete, and other contaminants from all types of vehicles.

STATE-OF-THE ART TECHNOLOGY: Overspray is removed with a gentle, advanced cleaning system which limits the use of razor blades, buffers, sandpaper, rubbing compounds, or clay products.

IMMEDIATE ACTION: Trained and uniformed technicians are mobilized quickly to handle your problems.

COMPLETE CLAIMS MANAGEMENT: Signed preinspection forms and release statements from satisfied claimants help to limit the liability of contractors and insurance companies.

Overspray Removal Specialists, Inc.

1-800-835-5858

www.sprayclaims.com

Click our Reader e-Card at paintsquare.com/ric

blastpak AIR-DRYING SYSTEMS

Moisture problems in your compressed-air lines?
FIGHT BACK WITH BLAST PAK!
Reduce downtime in all blasting and coating applications.

VAN AIR'S PORTABLE BLAST PAK AIR-DRYING SYSTEM

Your best choice
for moisture control
to prevent:

- air-line contamination
- flash rusting
- clogged blast pots
- system air loss
- air-line freeze ups

**FREE INITIAL FILL OF
DELIQUESCENT DESICCANT**



VAN AIR SYSTEMS



a division of Van Air, Inc.

1-800-840-9906

vanairsystems.com


©2007 Van Air, Inc.

Call our after-market sales team
for special discounts on
replacement desiccant
1-800-840-9906



**VAN AIR SYSTEMS IS YOUR FREEDOM
FROM MOISTURE-RELATED PROBLEMS.**

Click our Reader e-Card at paintsquare.com/ric

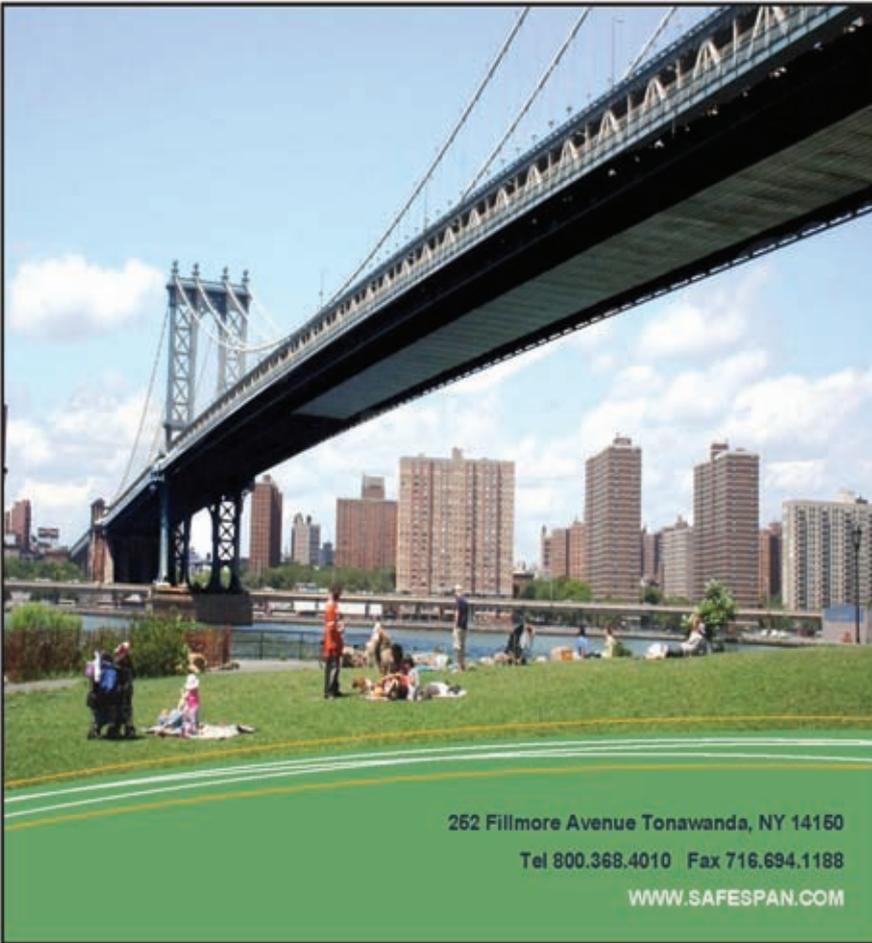

262 Fillmore Avenue Tonawanda, NY 14150

Tel 800.368.4010 Fax 716.694.1188

WWW.SAFESPAN.COM

EXPERIENCE

Nearly 15 years after pioneering the industry's most widely acclaimed platform system we continue to be the access solution of choice among the nation's top contractors.

QUALITY & SAFETY

A superior manufacturing facility with strict quality control methods and products that meet all OSHA & AASHTO requirements.


ENGINEERING & DESIGN

Complete in house engineering packages that have fast approval time and designs with accelerated installation in mind to save contractors expensive on-site labor costs.

INNOVATIVE & DIVERSE

With access as our only focus and with three different product lines we can provide solutions for any structure.

SAFESPAN

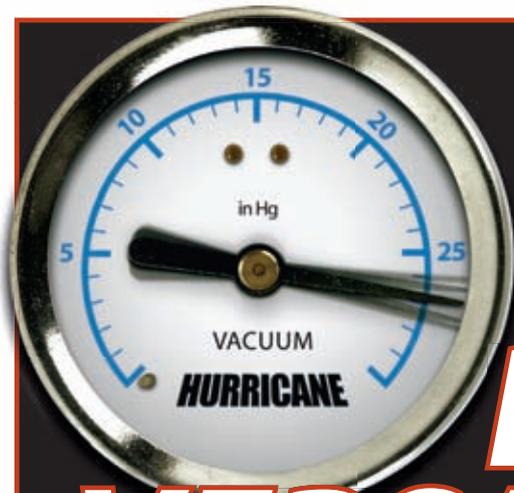

HURRICANE VACUUMS

POWER. VERSATILITY.

Setting The Quality Standard



HURRICANE 828

325 HP
5660 CFM
27" Mercury



HURRICANE 755

250 HP
3660 CFM
27" Mercury



HURRICANE 500

170 HP
2350 CFM
27" Mercury



Industrial Vacuum Equipment Corporation
N8091 Maple Street • Ixonia, WI 53036

1-800-331-4832

www.industrialvacuum.com



there is no subsequent need for shut-downs for re-lining floors, waste disposal, or downtime costs. Without being coated, the polymer concrete can have a service life of 20 or more years. Two possible concerns with polymer concretes are the cost per cubic foot and the weight per cubic foot.

Table 1 on p. 42 gives a relative and broad comparison of the properties, performance, and costs of the representative systems from the types discussed above. The purpose of this table is to provide a broad overview of generic types. Multiple factors need to be examined before to making a recommendation.

Summary

Applying a chemically resistant floor coating over concrete can be a complicated project. It requires attention to detail in the following five key steps outlined in this paper.

- Pre-project inspections
- Specification development
- Coating selection process
- Applicator selection process
- Establishment of and adherence to an appropriate QC/QA program

The design engineer has many options open to him or her in regards to a flooring system. He should make that choice in consultation with the coating manufacturer. Some systems will be inappropriate selections for one reason or another. The manufacturer can help sort through the various alternatives and help make a final coating selection.

When choosing a flooring system, there are several crucial elements that must be factored into the decision making process. Cost is simply not the only issue that one can use when deciding what is the most economical and beneficial flooring system for the

facility owner. Factors such as the degree of substrate degradation, surface preparation, everyday mechanical stresses imposed on the floor, chemical attack, and contractor competency play an ever-increasing role

in proper specification writing.

Choosing a trained and qualified contractor is also critical to the project's success. A poorly trained or unqualified applicator can result in problems all along the process and



We've got solutions.

The PreTox system renders heavy metal waste non-hazardous by RCRA standards, saving you money on disposal costs and reducing long-term liability.

The only abatement chemistry that works with all paint removal methods.

Our complete product line tailors the PreTox system to fit your needs.

Technical Contact: Dave Steffen • PreToxDave@aol.com
NexTec, Inc. • 800 338-8296 • www.PreTox.com

ULTRAHIGH-PRESSURE INDUSTRIAL CLEANING SOLUTIONS

Flow's 55,000 psi HUSKY® Industrial Cleaning Pump Raises the Bar in Productivity

Designed for **power**, and **built to last**, Flow's 55,000 psi HUSKY pump has set the new industry standard for both **productivity** and **reliability**, providing you with a portable ultrahigh-pressure waterjet pump that will **improve your bottom line**. The HUSKY is the **world's first** 55,000 psi direct drive triplex pump with full pressure compensation giving you the power you need to **reduce your operating costs** and **increase productivity on a square foot basis**.



To learn more call **800.446.FLOW** or visit **www.flowcorp.com**

 **Flow**

Click our Reader e-Card at paintsquare.com/ric

jeopardize the project's chance of success. A poorly written specification can ensure failure. The QC/QA process must be in place and fully operative before the project begins and it must be adhered to and enforced.

With a precise specification calling for proper preparation, testing, and flooring material, all parties involved in the flooring coating job will walk away knowing another long-lasting and quality floor was installed.



Lake H. Barrett, Sales Manager of Sauereisen Inc. (Pittsburgh, PA), is responsible for Sauereisen's domestic and international sales and service. He

is a graduate of Penn State University in mechanical engineering and has completed graduate work at Worcester Polytechnic Institute. He has over 20 years of experience with organic and inorganic polymer materials. Mr. Barrett has held positions in field services, technical support, sales and marketing. He is a member of SSPC, ASME, and NACE.



Heather M. Ramsey, chemist for Sauereisen, Inc., has been with the company for a little over two years. She received her M.S. in chemistry from The University of

Pittsburgh in 2006. Ms. Ramsey is involved in the research and development of both inorganic and organic corrosion-resistant materials as well as technical cements. She is a member of SSPC, Federation of Societies for Coatings Technology (FSCT), ASTM and the American Chemical Society (ACS).

THE LAST VACUUM YOU'LL EVER BUY

CONTRx Systems

No matter where your **DUST** comes from the **VORTEX-200** is ALL you need.

UNPRECEDENTED 3-YEAR FILTER WARRANTY

EQUIPMENT DEVELOPMENT CO., INC.
EDCO **CONTRx Systems**

Vortex 200

For More Information Visit: contrxsystems.com • 800-638-3326

Click our Reader e-Card at paintsquare.com/ric

Recommended Standards

- ASTM D4541, "Standard Test Method for Pull-Off Strength of Coatings Using Portable Adhesion Testers"
- ASTM C579, "Standard Test Method for Compressive Strength of Chemical-Resistant Mortar, Grouts, Monolithic Surfacing, and Polymer Concretes"
- ASTM C307, "Standard Test Method for Tensile Strength of Chemical-Resistant Mortar, Grouts, and Monolithic Surfacing"
- ASTM C580, "Standard Test Method for Flexural Strength and Modulus of Elasticity of Chemical-Resistant Mortars, Grouts, Monolithic Surfacing and Polymer Concretes"
- ASTM D2240, "Standard Test Method for Rubber Property—Durometer Hardness"
- ASTM D4060, "Standard Test Method for Abrasion Resistance of Organic Coatings by the Taber Abraser"
- ASTM D2047, "Standard Test Method for Static Coefficient of Friction of Polish-Coated Flooring Surfaces as Measured by the James Machine"
- ASTM D635, "Standard Test Method for Rate of Burning and/or Extent and Time of Burning of Plastics in a Horizontal Position"
- ASTM D 4263, "Standard Test Method for Indicating Moisture in Concrete by the Plastic Sheet Method"
- ASTM D4261, "Standard Practice for Surface Cleaning Concrete Unit Masonry for Coating"
- ASTM C279, "Standard Specification for Chemical-Resistant Masonry Units"
- ASTM C1160, "Standard Specification for Chemical-Resistant Carbon Brick"
- ASTM C126, "Standard Specification for Ceramic Glazed Structural Clay Facing Tile, Facing Brick, and Solid Masonry Units"
- SSPC-SP 12/NACE No. 5, "Surface Preparation and Cleaning of Metals by Waterjetting Prior to Recoating" (*although designed for steel, it is very informative for concrete applications)
- International Concrete Repair Institute (ICRI) No. 03732, "Guideline for Selecting and Specifying Concrete Surface Preparation for Sealers, Coatings, and Polymer Overlays"
- International Concrete Repair Institute (ICRI) No. 03730, "Guideline for Surface Preparation for the Repair of Deteriorated Concrete Resulting from Reinforcing Steel Corrosion"

JPCl

1949-2009
Celebrating 60 Years of Service to the Coatings Industry



KTA-Tator, Inc.
115 Technology Drive
Pittsburgh, PA 15275
PH-412.788.1300 • FX-412.788.1306
www.kta.com • www.ktagage.com

<p>KTA Chemists investigate coating failures and recommend repairs</p> <p>KTA Engineers recommend coating systems and prepare cleaning and painting specifications</p> <p>KTA EH&S Professionals evaluate worker and environmental exposures</p> <p>KTA Coatings Inspectors monitor cleaning and painting to verify specification compliance</p> <p>KTA Steel Inspectors monitor fabrication and erection to verify specification compliance</p> <p>KTA Educators provide lead, safety and coatings inspection training</p> <p>KTA Instrument Specialists supply all the testing equipment you may need</p>
--


Click our Reader e-Card at paintsquare.com/r/c

Industrial AG-Blower

for placing aggregate in unset base coats

The *Quikspray AG-Blower* will place quartz aggregate, sand, fillers, or non-skid granules at a rate up to 33# per minute into unset epoxy, cement, or poly basecoats. The applicator can cover 2500 sq. ft. without moving the *AG-Blower*. This unit will save significant labor, time, and materials as the application is more even and there is less product to remove.

- 115VAC, 60 hz
- Mobile
- Heavy-duty

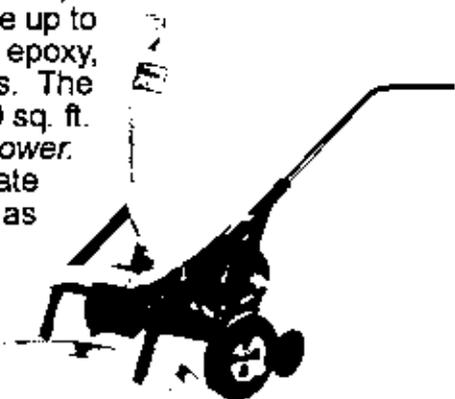

Quikspray, inc.

P.O. Box 327
Port Clinton, Oh 43452
ph (419) 732-2611
fx (419) 734-2628
www.quikspray.com

Click our Reader e-Card at paintsquare.com/r/c

Absolutely, positively, the fastest way to deliver color!™



chroma-chem 

Evonik. Power to create.


Click our Reader e-Card at paintsquare.com/ric



We proudly introduce Portfolio of Color™, our newest Industrial Color System, featuring over 2,700 colors. That's right — 2,700 colors! We have created an all-inclusive system that provides a reference guide for the colors and formulas most important to growing your industrial coatings business.

The Chroma-Chem® Color Identifier™ is a lightweight hand-held device that speeds the process of color selection in the field. Color Identifier™ simply locates the closest color match in the Portfolio of Color™, minimizing the time to locate a good color match.

Greater color choice and custom color selection has never been quicker and easier. Speeding the process increases efficiency, growth, profitability — and most important — your customer's satisfaction. Chroma-chem Portfolio of Color and Color Identifier....Absolutely, positively, the fastest way to deliver color!

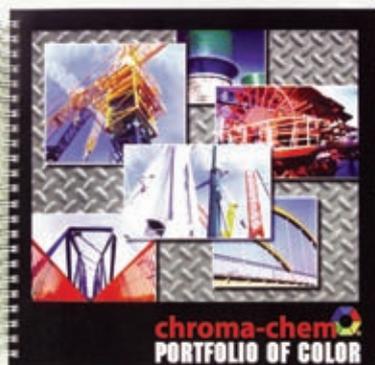

Chroma-Chem® ...The Future of Color Today™

For more information, please contact your local Evonik-Degussa account manager or the Industrial Colorants Marketing Group at 973-541-8958.
www.smartformulating.com



EVONIK
INDUSTRIES